

## Mechanical Buckling Analysis of Functionally Graded Plates Using a New Refined Theory

Mokhtar Bouazza<sup>1),2)</sup>, Khaled Amara<sup>2),3)</sup> and Nouredine Benseddiq<sup>4)</sup>

<sup>1)</sup> Department of Civil Engineering, University of Bechar, Bechar 08000, Algeria.  
E-Mail: bouazza\_mokhtar@yahoo.fr

<sup>2)</sup> Laboratory of Materials and Hydrology (LMH), University of Sidi Bel Abbes, Sidi Bel Abbes 2200, Algeria.

<sup>3)</sup> Department of Civil Engineering, University Centre of Ain Témouchent, Ain Témouchent 46000, Algeria

<sup>4)</sup> Mechanics Laboratory of Lille, CNRS UMR 8107, Ecole Polytech'Lille,  
University of Lille1, 59655 Villeneuve d'Ascq, France.

### ABSTRACT

In the present article, equilibrium and stability equations of rectangular functionally graded plates are determined using the new hyperbolic shear deformation theory. Unlike any other theory, the theory presented gives rise to only four governing equations. Number of unknown functions involved is only four, as against five in case of simple shear deformation theories of Mindlin and Reissner (first shear deformation theory). It is assumed that the material properties vary with the power product form of thickness coordinate variable  $z$ . The equilibrium and stability equations are employed to study the buckling behavior of functionally graded plates with all edges simply supported and subjected to in-plane loading conditions. The results obtained are compared with their counterparts in the literature.

**KEYWORDS:** New plate theory, Shear deformable plate theory, Functionally graded plates, Mechanical buckling.

### INTRODUCTION

Recent studies on new performance materials have treated new composite materials known as Functionally Graded Materials (FGMs). These are high-performance heat-resistant materials able to withstand ultrahigh temperatures and extremely large gradients used in spacecrafts and nuclear plants. FGMs are microscopically inhomogeneous composite materials in which the mechanical properties vary smoothly and continuously from one surface to the other (Suresh and Mortensen, 1998). These novel materials were first introduced by a group of scientists in Sendai, Japan in

1984 (Koizumi, 1997) and then developed by other scientists (Koizumi and Niino, 1995; Kaysser and Ilschner, 1995). Typically, these materials are made from a mixture of ceramics and metal. It is apparent from the literature that most of the research on FGMs has been restricted to thermal stress analysis, fracture mechanics and optimization. Very little work has been done that considers stability analysis, buckling and vibrational behavior of structures made of functionally graded materials.

FG plate problems deal with two main concepts: the modeling of the plate (plate theories) and the procedure of solution. Most commonly used plate theories can be classified into three main categories: thin plate theory (Leissa, 1973; Yu, 2008; Bouazza and Adda-Bedia, 2013; Meisam et al., 2009) (e.g. Kirchhoff theory or

---

Received on 14/5/2015.

Accepted for Publication on 31/5/2015.

CPT), moderately thick plate theory (Reissner, 1945; Reissner, 1944; Mindlin, 1951; Bouazza et al., 2009; Bouazza et al., 2010; Praveen and Reddy, 1998) (e.g. first-order shear deformation plate theory of Mindlin or FSDT) and thick plate theory (Reddy and Phan, 1985; Reddy, 1984; Hanna and Leissa, 1994; Zhou et al., 2002) (e.g. third-order shear deformation plate theory of Reddy or TSDT, higher-order shear deformation plate theory or HSDT and three-dimensional (3-D) elasticity theory).

Different higher-order shear deformation plate theories (HSDTs) were proposed, including the second-order shear deformation formulation of Whitney and Sun (1973) and the third-order shear deformation theory of Lo et al. (1977) with 11 unknowns; Kant (1982) with six unknowns; Bhimaraddi and Stevens (1984) with five unknowns; Reddy (1985, 1984) with five unknowns and Hanna and Leissa (1994) with four unknowns. Ambartsumian (1958) proposed a transverse shear stress function in order to explain plate deformation. A similar method was used later by Soldatos and Timarci (1993) for dynamic analysis of laminated shells. Later, some new functions were proposed by Reddy (1984), Touratier (1991), Karama et al. (2003), Soldatos (1992) and Aydogdu (2009).

An alternative variational theorem; namely the Reissner Mixed Variational Theorem (RMVT), was proposed by Reissner (1984; 1986) for the analysis of laminated composite plates, where the displacement and transverse stress components are regarded as the primary variables and the in-plane stress components can be calculated by the primary variables that are determined. The related developments, ideas and evaluations based on the RMVT with regard to the modeling of multi-layered plates and shells were precisely described by Carrera (2001). Based on the RMVT, Murakami (1986) and Toledano and Murakami (1987) proposed the mixed laminated plate theories with first-order and higher-order zigzag displacement models, respectively, to improve the in-plane responses of the laminated composite plates. Carrera (2003) presented a historical review of zigzag theories of

multi-layered plates and shells. Carrera (2000, 2000) also presented the assessments of mixed and classical theories on global and local responses of multi-layered orthotropic plates and concluded that the RMVT-based theories are superior to the PVD-based ones after implementations and comparisons among more than 40 theories were undertaken.

Recently, a two-variable refined plate theory (RPT) was first developed for isotropic plates by Shimpi (2002) and was extended to orthotropic plates by Shimpi and Patel (2006, 2006) and Kim et al. (2009) and was extended to functionally graded plates by Mechab et al. (2010) and Thai and Choi (2012).

In the present article, equilibrium and stability equations for the rectangular functionally graded plates are obtained on the basis of new hyperbolic shear deformation theory. Resulting equations are employed to analyze the buckling behavior and obtain the critical buckling loads. In order to establish the fundamental system of equations for the buckling analysis, we assume that the non-homogeneous mechanical properties are given by the power product form of coordinate variable  $z$ .

## Problem Formulation

### Material Properties

Consider a rectangular plate of total thickness  $h$  as shown in Fig. 1. The plate FGM is made of ceramic and metal and the material properties of FGM vary continuously across the thickness according to the following equations, which are the same as the equations proposed by Praveen and Reddy (1998).

$$\begin{aligned} E(z) &= E_m + E_{cm} V_f(z) & E_{cm} &= E_c - E_m \\ v(z) &= v_0 \end{aligned} \quad (1)$$

For simplicity, Poisson's ratio of the plate is assumed to be constant in this study, as the effect of Poisson's ratio on deformation is much less than that of Young's modulus (Delale and Erdogan, 1983).

Subscripts  $m$  and  $c$  refer to properties of metal and ceramics, respectively and  $V_f(z)$  is the volume fraction of the constituents which can mostly be

defined by power-law functions (Yu, 2008; Bouazza and Adda-Bedia, 2013; Meisam et al., 2009; Bouazza et al., 2009; Praveen and Reddy, 1998). For power-law

FGM, the volume fraction function is expressed as:

$$V_f(z) = (z/h + 1/2)^k \tag{2}$$

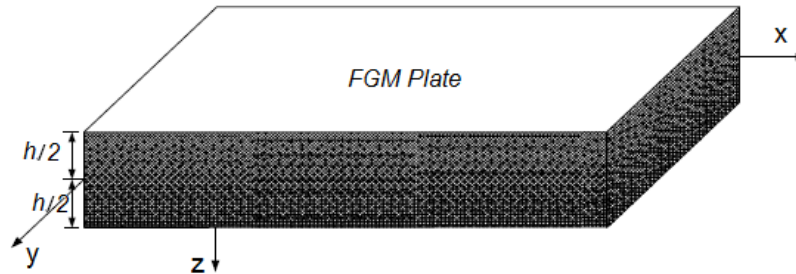


Figure (1): Typical FGM rectangular plate

**Higher-Order Plate Theories with Five Unknown Functions**

The displacements of a material point located at (x, y, z) in the plate may be written as:

$$\begin{aligned} U(x,y,z) &= u_0(x,y) - z \frac{\partial w_0}{\partial x} + \Psi(z)\theta_x \\ V(x,y,z) &= v_0(x,y) - z \frac{\partial w_0}{\partial y} + \Psi(z)\theta_y \\ W(x,y,z) &= w_0(x,y) \end{aligned} \tag{3}$$

where  $U, V$  and  $W$  are the displacements in the x, y and z directions,  $u_0, v_0$  and  $w_0$  are the midplane displacements and  $\theta_x$  and  $\theta_y$  are the rotations of the yz and xz planes due to bending, respectively.  $\Psi(z)$  represents shape function determining the distribution of the transverse shear strains and stresses along the thickness. The description of various displacement models is given in Appendix 1.

**Present New Hyperbolic Shear Deformation Theory**

Unlike the other theories, the number of unknown functions involved in the present refined hyperbolic shear deformation theory is only four, as against five in case of other shear deformation theories (Reissner, 1984; Reissner, 1986; Carrera, 2001; Murakami, 1986; Toledano and Murakami, 1987; Carrera, 2003; Carrera, 2000; Carrera, 2000). The theory presented is variationally consistent, does not require shear

correction factor and gives rise to transverse shear stress variation such that the transverse shear stresses vary parabolically across the thickness, satisfying shear stress free surface conditions.

**Assumptions of the Present Plate Theory**

Assumptions of the present theory are as follows:

- (i) The displacements are small in comparison with the plate thickness and, therefore, strains involved are infinitesimal.
- (ii) The transverse displacement  $W$  includes two components of bending  $w_b$  and shear  $w_s$ . Both these components are functions of coordinates x and y.
- (iii) The transverse normal stress  $\sigma_z$  is negligible in comparison with in-plane normal stresses  $\sigma_x$  and  $\sigma_y$ .
- (iv) The in-plane displacements  $U$  and  $V$  consist of extension, bending and shear components.

$$W(x,y,z) = w_b(x,y) + w_s(x,y) \tag{4}$$

The bending components  $u_b$  and  $v_b$  are assumed to be similar, respectively, to the displacements given by the classical plate theory. Therefore, the expression for  $u_b$  and  $v_b$  can be given as:

$$u_b = -z \frac{\partial w_b}{\partial x} \text{ and } v_b = -z \frac{\partial w_b}{\partial y} \tag{6}$$

The shear components  $u_s$  and  $v_s$  give rise, in

conjunction with  $w_s$ , to the parabolic variations of shear strains  $\gamma_{xz}, \gamma_{yz}$  and hence to shear stresses  $\sigma_{xz}, \sigma_{yz}$  through the thickness of the plate in such a way that shear stresses  $\sigma_{xz}, \sigma_{yz}$  are zero at the top and bottom faces of the plate. Consequently, the expression for  $u_s$  and  $v_s$  can be given as:

$$u_s = -f(z) \frac{\partial w_s}{\partial x} \quad \text{and} \quad v_s = -f(z) \frac{\partial w_s}{\partial y} \quad (7)$$

### Kinematics and Constitutive Equations

Based on the assumptions made in the preceding section, the displacement field of the present theory can be obtained using Eqs. (4)–(7) as:

$$\begin{aligned} U(x, y, z) &= u_0(x, y) - z \frac{\partial w_b}{\partial x} - f(z) \frac{\partial w_s}{\partial x} \\ V(x, y, z) &= v_0(x, y) - z \frac{\partial w_b}{\partial y} - f(z) \frac{\partial w_s}{\partial y} \\ W(x, y, z) &= w_b(x, y) + w_s(x, y) \end{aligned} \quad (8)$$

where:

$$f(z) = \frac{(h/\pi) \sinh\left(\frac{\pi}{h} z\right) - z}{[\cosh(\pi/2) - 1]} \quad (9)$$

It should be noted that unlike the first-order shear deformation theory, this theory does not require shear correction factors. The kinematic relations can be obtained as follows:

$$\begin{aligned} \varepsilon_x &= \varepsilon_x^0 + zk_x^b + f(z)k_x^s \\ \varepsilon_y &= \varepsilon_y^0 + zk_y^b + f(z)k_y^s \\ \gamma_{xy} &= \gamma_{xy}^0 + zk_{xy}^b + f(z)k_{xy}^s \\ \gamma_{yz} &= g(z)\gamma_{yz}^s \\ \gamma_{xz} &= g(z)\gamma_{xz}^s \\ \varepsilon_z &= 0 \end{aligned} \quad (10)$$

where:

$$\begin{aligned} \varepsilon_x^0 &= \frac{\partial u}{\partial x}, \quad k_x^b = -\frac{\partial^2 w_b}{\partial x^2}, \quad k_x^s = -\frac{\partial^2 w_s}{\partial x^2} \\ \varepsilon_y^0 &= \frac{\partial v}{\partial y}, \quad k_y^b = -\frac{\partial^2 w_b}{\partial y^2}, \quad k_y^s = -\frac{\partial^2 w_s}{\partial y^2} \\ \gamma_{xy}^0 &= \frac{\partial u}{\partial y} + \frac{\partial v}{\partial x}, \quad k_{xy}^b = -2 \frac{\partial^2 w_b}{\partial x \partial y}, \quad k_{xy}^s = -2 \frac{\partial^2 w_s}{\partial x \partial y} \\ \gamma_{yz}^s &= \frac{\partial w_s}{\partial y}, \quad \gamma_{xz}^s = \frac{\partial w_s}{\partial x} \\ g(z) &= 1 - f'(z), \quad f'(z) = \frac{df(z)}{dz} \end{aligned} \quad (11)$$

The results of the mathematical derivations are given in Appendix 2.

The linear constitutive relations of an FGM plate can be written as:

$$\begin{Bmatrix} \sigma_x \\ \sigma_y \\ \sigma_{xy} \\ \sigma_{yz} \\ \sigma_{xz} \end{Bmatrix} = \begin{bmatrix} Q_{11} & Q_{12} & 0 & 0 & 0 \\ Q_{12} & Q_{22} & 0 & 0 & 0 \\ 0 & 0 & Q_{66} & 0 & 0 \\ 0 & 0 & 0 & Q_{44} & 0 \\ 0 & 0 & 0 & 0 & Q_{55} \end{bmatrix} \begin{Bmatrix} \varepsilon_x \\ \varepsilon_y \\ \gamma_{xy} \\ \gamma_{yz} \\ \gamma_{xz} \end{Bmatrix} \quad (12)$$

where:

$$\begin{aligned} Q_{11} = Q_{22} &= \frac{E(z)}{1-\nu^2}, \quad Q_{12} = \nu Q_{11}, \quad Q_{44} = Q_{55} = \\ Q_{66} &= \frac{E(z)}{2(1+\nu)} \end{aligned} \quad (13)$$

### Governing Equations

The strain energy of the plate can be written as:

$$\begin{aligned} U &= \frac{1}{2} \int_V \sigma_{ij} \varepsilon_{ij} dV = \\ &= \frac{1}{2} \int_V (\sigma_x \varepsilon_x + \sigma_y \varepsilon_y + \sigma_{xy} \gamma_{xy} + \sigma_{yz} \gamma_{yz} + \sigma_{xz} \gamma_{xz}) dV \end{aligned} \quad (14)$$

The principle of virtual work for the present problem may be expressed as follows:

$$\iint [N_x \delta \varepsilon_x^0 + N_y \delta \varepsilon_y^0 + N_{xy} \delta \gamma_{xy}^0 + M_x^b \delta k_x^b + M_y^b \delta k_y^b + M_{xy}^b \delta k_{xy}^b + M_x^s \delta k_x^s + M_y^s \delta k_y^s + M_{xy}^s \delta k_{xy}^s + Q_{yz} \delta \gamma_{yz} + Q_{xz} \delta \gamma_{xz}] dxdy = 0 \quad (15)$$

where  $(N_x, N_y, N_{xy})$  denote the total in-plane force resultants,  $(M_x^b, M_y^b, M_{xy}^b)$ ,  $(M_x^s, M_y^s, M_{xy}^s)$  denote the total moment resultants and  $(Q_{xz}, Q_{yz})$  are transverse shear stress resultants and they are defined as:

$$\begin{aligned} (N_x, N_y, N_{xy}) &= \int_{-h/2}^{h/2} (\sigma_x, \sigma_y, \sigma_{xy}) dz \\ (M_x^b, M_y^b, M_{xy}^b) &= \int_{-h/2}^{h/2} (\sigma_x, \sigma_y, \sigma_{xy}) z dz \\ (M_x^s, M_y^s, M_{xy}^s) &= \int_{-h/2}^{h/2} (\sigma_x, \sigma_y, \sigma_{xy}) f(z) dz \\ (Q_{xz}, Q_{yz}) &= \int_{-h/2}^{h/2} (\sigma_{xz}, \sigma_{yz}) g(z) dz \end{aligned} \tag{16}$$

Substituting Eq. (12) into Eq. (16) and integrating

$$\begin{aligned} \{N\} &= \{N_x, N_y, N_{xy}\}^t, \quad \{M^b\} = \{M_x^b, M_y^b, M_{xy}^b\}^t, \quad \{M^s\} = \{M_x^s, M_y^s, M_{xy}^s\}^t \\ \{\epsilon^0\} &= \{\epsilon_x^0, \epsilon_y^0, \gamma_{xy}^0\}^t, \quad \{k^b\} = \{k_x^b, k_y^b, k_{xy}^b\}^t, \quad \{k^s\} = \{k_x^s, k_y^s, k_{xy}^s\}^t \end{aligned} \tag{18}$$

and  $A_{ij}, B_{ij}, \dots$  etc. are the plate stiffness, defined by:

$$\begin{aligned} (A_{ij}, B_{ij}, D_{ij}, B_{ij}^s, D_{ij}^s, H_{ij}^s) &= \int_{-h/2}^{h/2} Q_{ij}(1, z, z^2, f(z), zf(z), (f(z))^2) dz \quad (i, j = 1, 2, 6) \\ A_{ij}^s &= \int_{-h/2}^{h/2} Q_{ij}(g(z))^2 dz \quad (i, j = 4, 5) \end{aligned} \tag{19}$$

The stability equations of the plate may be derived by the adjacent equilibrium criterion. Assume that the equilibrium state of the FGM plate under thermal loads is defined in terms of the displacement components  $(u_0^0, v_0^0, w_b^0, w_s^0)$ . The displacement components of a neighboring stable state differ by  $(u_0^1, v_0^1, w_b^1, w_s^1)$  with respect to the equilibrium position. Thus, the total displacements of a neighboring state are:

$$u_0 = u_0^0 + u_0^1, \quad v_0 = v_0^0 + v_0^1, \quad w_b = w_b^0 + w_b^1, \quad w_s = w_s^0 + w_s^1 \tag{20}$$

where the superscript 1 refers to the state of stability and the superscript 0 refers to the state of equilibrium conditions.

Substituting Equations (10), (11) and (20) into Equation (15) and integrating by parts and then equating the coefficients of  $\delta u_0^1, \delta v_0^1, \delta w_b^1$  and  $\delta w_s^1$  to zero, separately, the governing stability equations are obtained for the shear deformation plate theories as:

through the thickness of the plate, the stress resultants are given as:

$$\begin{Bmatrix} \{N\} \\ \{M^b\} \\ \{M^s\} \end{Bmatrix} = \begin{bmatrix} [A] & [B] & [B^s] \\ [B] & [D] & [D^s] \\ [B^s] & [D^s] & [H^s] \end{bmatrix} \begin{Bmatrix} \{\epsilon^0\} \\ \{k^b\} \\ \{k^s\} \end{Bmatrix} \tag{17a}$$

$$\begin{Bmatrix} Q_{yz} \\ Q_{xz} \end{Bmatrix} = \begin{bmatrix} A_{44}^s & 0 \\ 0 & A_{55}^s \end{bmatrix} \begin{Bmatrix} \gamma_{yz}^s \\ \gamma_{xz}^s \end{Bmatrix} \tag{17b}$$

where:

$$\begin{aligned} \frac{\partial N_x^1}{\partial x} + \frac{\partial N_{xy}^1}{\partial y} &= 0 \\ \frac{\partial N_{xy}^1}{\partial x} + \frac{\partial N_y^1}{\partial y} &= 0 \\ \frac{\partial^2 M_x^{b1}}{\partial x^2} + 2 \frac{\partial^2 M_{xy}^{b1}}{\partial x \partial y} + \frac{\partial^2 M_y^{b1}}{\partial y^2} + \bar{N} &= 0 \\ \frac{\partial^2 M_x^{s1}}{\partial x^2} + 2 \frac{\partial^2 M_{xy}^{s1}}{\partial x \partial y} + \frac{\partial^2 M_y^{s1}}{\partial y^2} + \frac{\partial Q_{xz}^{s1}}{\partial x} + \frac{\partial Q_{yz}^{s1}}{\partial y} + \bar{N} &= 0 \end{aligned} \tag{21}$$

with:

$$\begin{aligned} \bar{N} &= N_x^0 \frac{\partial^2 (w_b^1 + w_s^1)}{\partial x^2} + N_y^0 \frac{\partial^2 (w_b^1 + w_s^1)}{\partial y^2} + \\ &2N_{xy}^0 \frac{\partial^2 (w_b^1 + w_s^1)}{\partial x \partial y} \end{aligned} \tag{22}$$

Clearly, when the effect of transverse shear deformation is neglected ( $w_s = 0$ ), the governing

equation (21) yields the governing equation of FGM plate based on the classical plate theory.

**Navier Solution for Simply Supported Rectangular Plates**

Rectangular plates are generally classified in accordance with the type of support used. We are here concerned with the exact solution of Equations (21) for a simply supported FGM plate. The following boundary conditions are imposed for the present refined plate theory at the side edges:

$$v_0^l = w_b^l = w_s^l = \frac{\partial w_s^l}{\partial y} = N_x^l = M_x^{bl} = M_x^{sl} = 0, \text{ at } x=0, a \tag{23a}$$

$$u_0^l = w_b^l = w_s^l = \frac{\partial w_s^l}{\partial x} = N_y^l = M_y^{bl} = M_y^{sl} = 0, \text{ at } y=0, b \tag{23b}$$

Based on the Navier method, the following approximate solution is seen to satisfy both the differential equation and the boundary conditions:

$$\begin{Bmatrix} u_0^l \\ v_0^l \\ w_b^l \\ w_s^l \end{Bmatrix} = \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} \begin{Bmatrix} U_{mn}^l \cos \lambda x \sin \mu y \\ V_{mn}^l \sin \lambda x \sin \mu y \\ W_{bmn}^l \sin \lambda x \sin \mu y \\ W_{smn}^l \sin \lambda x \sin \mu y \end{Bmatrix} \tag{24}$$

where  $U_{mn}^l, V_{mn}^l, W_{bmn}^l, W_{smn}^l$  are arbitrary parameters to be determined and  $\lambda = m\pi/a$  and  $\mu = n\pi/b$ .

Substituting Eq. (24) into Eq.(21) and using the derivation of new Eq. (21) given in Appendix 3,

$$[S]\{A\} = 0 \tag{25}$$

where  $\{A\}$  denotes the column  $\{A\} = \{U_{mn}^l, V_{mn}^l, W_{bmn}^l, W_{smn}^l\}^t$  (26)

and  $[S]$  is the symmetric matrix given by:

$$\begin{bmatrix} s_{11} & s_{12} & s_{13} & s_{14} \\ s_{12} & s_{22} & s_{23} & s_{24} \\ s_{13} & s_{23} & s_{33} & s_{34} \\ s_{14} & s_{24} & s_{34} & s_{44} \end{bmatrix} \tag{27}$$

in which:

$$\begin{aligned} s_{11} &= A_{11}\lambda^2 + A_{66}\mu^2, & s_{12} &= \lambda\mu(A_{12} + A_{66}), & s_{22} &= A_{66}\lambda^2 + A_{22}\mu^2, \\ s_{13} &= -\lambda[B_{11}\lambda^2 + (B_{12} + 2B_{66})\mu^2], & s_{14} &= -\lambda[B_{11}^s\lambda^2 + (B_{12}^s + 2B_{66}^s)\mu^2], \\ s_{23} &= -\mu[(B_{12} + 2B_{66})\lambda^2 + B_{22}\mu^2], & s_{24} &= -\mu[(B_{12}^s + 2B_{66}^s)\lambda^2 + B_{22}^s\mu^2], \\ s_{33} &= D_{11}\lambda^4 + 2(D_{12} + 2D_{66})\lambda^2\mu^2 + D_{22}\mu^4 + N_x^0\lambda^2 + N_y^0\mu^2 \\ s_{34} &= D_{11}^s\lambda^4 + 2(D_{12}^s + 2D_{66}^s)\lambda^2\mu^2 + D_{22}^s\mu^4 + N_x^0\lambda^2 + N_y^0\mu^2 \\ s_{44} &= H_{11}^s\lambda^4 + 2(H_{12}^s + 2H_{66}^s)\lambda^2\mu^2 + H_{22}^s\mu^4 + A_{55}^s\lambda^2 + A_{44}^s\mu^2 + N_x^0\lambda^2 + N_y^0\mu^2 \end{aligned} \tag{28}$$

The results of the mathematical derivations are given in Appendix 3.

By applying the condensation approach to eliminate the in-plane displacements  $U_{mn}^l$  and  $V_{mn}^l$ , Eq. (25) can be rewritten as:

$$[\bar{S}]\{\bar{A}\} = 0 \tag{29}$$

where:

$$[\bar{S}] = \begin{bmatrix} \bar{S}_{33} & \bar{S}_{43} \\ \bar{S}_{43} & \bar{S}_{44} \end{bmatrix} \tag{30}$$

$$\{\bar{A}\} = \begin{Bmatrix} W_{bmn} \\ W_{smn} \end{Bmatrix}$$

and

$$\begin{aligned} \bar{s}_{33} &= s_{33} - s_{13} \frac{b_1}{b_0} - s_{23} \frac{b_2}{b_0} + N_x^0 (\lambda^2 + \mu^2), \bar{s}_{34} = s_{34} - s_{14} \frac{b_1}{b_0} - s_{24} \frac{b_2}{b_0} + N_x^0 (\lambda^2 + \mu^2), \\ \bar{s}_{43} &= s_{34} - s_{13} \frac{b_3}{b_0} - s_{23} \frac{b_4}{b_0} + N_x^0 (\lambda^2 + \mu^2), \bar{s}_{44} = s_{44} - s_{14} \frac{b_3}{b_0} - s_{24} \frac{b_4}{b_0} + N_x^0 (\lambda^2 + \mu^2), \end{aligned} \tag{31}$$


$$b_0 = s_{11}s_{22} - s_{12}^2, b_1 = s_{13}s_{22} - s_{12}s_{23}, b_2 = s_{11}s_{23} - s_{12}s_{13}, b_3 = s_{14}s_{22} - s_{12}s_{24}, b_4 = s_{11}s_{24} - s_{12}s_{14}$$

**Mechanical Buckling Analysis**

Consider a rectangular plate with the length a and width b which is subjected to in-plane loads. Therefore, the pre-buckling forces can be obtained using the equilibrium conditions as (Yu, 2008; Bouazza and Adda-Bedia, 2013; Meisam et al., 2009):

$$N_x^0 = \xi_1 N_0, N_y^0 = \xi_2 N_0, N_{xy}^0 = 0 \tag{32}$$

where  $N_0$  is the force per unit length,  $\xi_1$  and  $\xi_2$  are the load parameters which indicate the loading conditions. Negative values for  $\xi_1$  and  $\xi_2$  indicate that the plate is subjected to biaxial compressive loads, while positive values are used for tensile loads. Also, zero value for  $\xi_1$  or  $\xi_2$  shows uniaxial loading in x or y directions, respectively, as shown in Fig. 2.

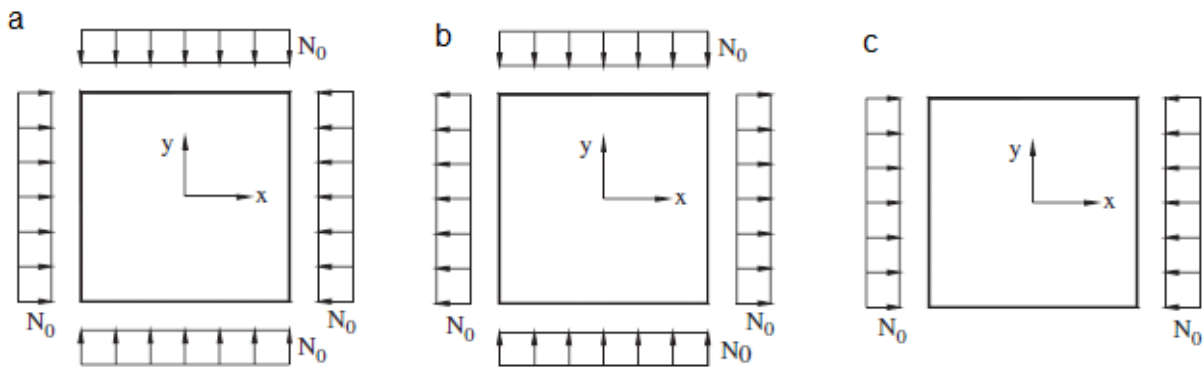

**Figure (2): The loading conditions of rectangular plate for (a) biaxial compression (b) tension in the x direction and compression in the y direction and (c) uniaxial compression**

Substituting Eq. (32) into Eq. (30), for non-trivial solution, the determinant of the coefficient matrix in new Eq. (30) must be zero. This gives the following expression for buckling load:

$$N_{cr}(m, n) = \frac{-I}{\xi_1 \lambda^2 + \xi_2 \mu^2} \frac{\bar{S}_{33}\bar{S}_{44} - \bar{S}_{34}\bar{S}_{43}}{\bar{S}_{33} + \bar{S}_{44} - \bar{S}_{34} - \bar{S}_{43}} \tag{33}$$

For each choice of m and n, there is a corresponsive unique value of  $N_{cr}$ . The critical buckling load is the smallest value of  $N_{cr}(m, n)$ .

**RESULTS AND DISCUSSION**

In this section, various numerical examples are presented and discussed for verifying the accuracy and efficiency of the present theory in predicting the critical buckling load of FGM plates subjected to in-plane loading. For the verification purpose, the results obtained by the present theory are compared with those found in the literature using CPT, FSDT and HSDT. The following material properties are used:

Material 1 (Al=Al<sub>2</sub>O<sub>3</sub>):  $E_c = 380 \text{ GPa}, E_m = 70 \text{ GPa}, \nu = 0.3$

Material 2 (Al=SiC):  $E_c = 420 \text{ GPa}, E_m = 70 \text{ GPa}, \nu = 0.3$

**Comparisons**

In order to validate the accuracy of the present method, a comparison has been carried out with previously published results by Mizusawa (1993), Hosseini-Hashemi et al. (2008), Shufrin and Eisenberger (2005) and Xiang (1993) for both thin

(h/a=0.001) and moderately thick, simply supported square rectangular plates. Plates are subjected to monoaxial, in-plane compressive applied loads in the x ( $\xi_1 = -1, \xi_2 = 0$ ) and equal biaxial, in-plane compressive applied loads ( $\xi_1 = -1, \xi_2 = -1$ ). Comparison results are shown in Tables 1 and 2.

**Table 1. Comparison study of buckling load parameters,  $\tilde{N}_{cr}/\pi^2 = N_{cr}a^2/\pi^2 D$  for simply supported isotropic square plates subjected to monoaxial in-plane compressive applied loads in the x direction ( $\xi_1 = -1, \xi_2 = 0$ )**

Method	h/a			
	0.001	0.05	0.1	0.2
Mizusawa (1993)	4	(3.928)	(3.729)	(3.119)
Mizusawa (1993)	4	3.944	3.784	3.256
Hosseini-Hashemi et al. (2008) <sup>a</sup>	4	3.9437	3.7838	3.2558
Shufrin and Eisenberger (2005)	–	–	3.7865	3.2637
Hosseini-Hashemi et al. (2008) <sup>b</sup>	4	3.9444	3.7864	3.2637
Present theory	4	3.9444	3.7868	3.2656

( ) Considering higher-order shear strain.

<sup>a</sup> Shear correction factor  $k^2 = \pi^2/12$ .

<sup>b</sup> Shear correction factor  $k^2 = 5/6$ .

**Table 2. Comparison study of buckling load parameters,  $\tilde{N}_{cr}/\pi^2 = N_{cr}a^2/\pi^2 D$ , for simply supported isotropic square plates subjected to equal biaxial in-plane compressive applied loads ( $\xi_1 = -1, \xi_2 = -1$ )**

Method	h/a				
	0.001	0.005	0.05	0.1	0.2
Xiang (1993)	2	–	1.9719	1.8920	1.7723
Hosseini-Hashemi et al. (2008) <sup>a</sup>	2	1.9997	1.9718	1.8919	1.7722
Present theory	2	1.9997	1.9722	1.8934	1.6328

<sup>a</sup> Shear correction factor  $k^2 = 0.823045$ .

The buckling load parameters  $\tilde{N}_{cr}/\pi^2$  are listed in Table 1 for h/a= 0.001, 0.05, 0.1 and 0.2 together with the available results by Mizusawa (1993), obtained by using the spline strip method, by Shufrin and Eisenberger (2005), obtained by using the Levy method and Hosseini-Hashemi et al. (2008), obtained by exact solution of rectangular Mindlin plates. An excellent agreement can be observed between the present results and those given by Shufrin and Eisenberger (2005) and Hosseini-Hashemi et al.

(2008). Good agreement has also been achieved between the present results and those of Mizusawa (1993). Note that higher-order terms (in the transverse shear strain) have been considered in Mizusawa’s (1993) study. Those results are shown in parentheses in Table 1 to distinguish them from the rest of results. Full agreement of the present results for simply supported plates subjected to equal biaxial in-plane compressive loads ( $\xi_1 = -1, \xi_2 = -1$ ) exists with the solution of Xiang (1993), obtained by using the pb-2



Rayleigh–Ritz method and Hosseini-Hashemi et al. (2008) for shear correction factor  $k^2 = 0.823045$ . This is shown in Table 2 for both thin and moderately thick square plates. As Table 2 shows, the present results have good agreement with Hosseini-Hashemi et al. (2008) and Xiang (1993).

In addition, the comparison in Tables 1 and 2 shows that the results of the present theory have similar responses with both biaxial and uniaxial compression in all material cases. However, the critical buckling load parameters under biaxial compression are twice those under uniaxial compression.

The next comparison is performed for simply supported plates subjected to various loading conditions. The plate is made from a mixture of Aluminum (Al) and Silicon Carbide (SiC). The critical buckling loads of simply supported plate for different values of thickness ratio  $b/h$ , aspect ratio  $a/b$  and power law index  $k$  are shown in Table 3. It can be seen that the critical buckling load of the present theory is almost identical with those reported by Bodaghi and Saidi (2010) based on HSDT and Thai and Choi (2012) based on RPT. The changes of critical buckling mode of FGM plate predicted by the present theory as well as by HSDT and RPT are identical. In addition, it can be seen that the critical buckling load decreases as the

power law index increases and the variation of the critical buckling load is considerable when the power law index is small. This is due to the fact that higher values of power law index correspond to high portion of metal in comparison with the ceramic part. In all material cases, the critical buckling increases when the geometric parameter  $b/h$  is increased. Moreover, increasing thickness ratio not only increases the values of critical buckling load, but also causes the changes in critical buckling mode. On the other hand, the critical buckling plate load under uniaxial compression ( $\xi_1 = -1, \xi_2 = 0$ ) is greater than that under biaxial compression ( $\xi_1 = -1, \xi_2 = -1$ ) and less than that under biaxial compression and tension ( $\xi_1 = -1, \xi_2 = 1$ ).

It should be noted that the present theory involves only four independent variables as against five in the case of HSDT (1993) and FSDT (Misuzawa, 1993; Hosseini-Hashemi et al., 2008; Shufrin and Eisenberger, 2005; Xiang, 1993). Also, the present theory does not require shear correction factors as in the case of FSDT. It can be concluded that the present theory is not only accurate, but also efficient in predicting the critical buckling loads of FG plates compared to other shear deformation plate theories, such as FSDT and HSDT.

**Table 3. Comparison of critical buckling load (MN/m) of simply supported Al/SiC plate**

$(\xi_1, \xi_2)$	a/b	b/h	Method	k		
				0	1	2
(-1,0)	0.5	10	HSDT [49]	2079.721	1028.412	780.097
			RPT [43]	2079.758	1028.449	780.023
			Present	2079.926	1028.519	780.489
		5	HSDT [49]	12162.119	6270.298	4692.542
			RPT [43]	12164.987	6272.425	4695.029
			Present	12164.156	6272.046	4698.211
(-1,0)	1	10	HSDT [49]	1437.361	702.304	534.441
			RPT [43]	1437.389	702.251	534.835
			Present	1437.453	702.277	534.917
		5	HSDT [49]	9915.620	4955.431	3746.054
			RPT [43]	9916.193	4955.484	3746.732
			Present	9917.076	4955.862	3748.490
		10	HSDT [49]	1527.903 <sup>a</sup>	748.920 <sup>a</sup>	569.751 <sup>a</sup>
			RPT [43]	1527.994 <sup>a</sup>	748.988 <sup>a</sup>	569.825 <sup>a</sup>

(-1,0)	1.5		Present	1528.080 <sup>a</sup>	749.023 <sup>a</sup>	569.942 <sup>a</sup>
		5	HSDT [49]	10044.721 <sup>a</sup>	5067.219 <sup>a</sup>	3819.109 <sup>a</sup>
			RPT [43]	10044.962 <sup>a</sup>	5068.084 <sup>a</sup>	3820.079 <sup>a</sup>
			Present	10045.701 <sup>a</sup>	5068.407 <sup>a</sup>	3822.248 <sup>a</sup>
(-1,-1)	0.5	10	HSDT [49]	1663.777	822.738	624.158
			RPT [43]	1663.807	822.759	624.182
			Present	1663.941	822.815	624.391
	5	HSDT [49]	9729.999	5016.384	3754.274	
		RPT [43]	9731.990	5017.941	3756.023	
		Present	9731.325	5017.637	3758.569	
(-1,-1)	1	10	HSDT [49]	718.692	351.124	267.416
			RPT [43]	718.695	351.125	267.418
			Present	718.726	351.138	267.459
	5	HSDT [49]	4957.888	2477.589	1873.190	
		RPT [43]	4958.097	2477.742	1873.366	
		Present	4958.538	2477.931	1874.245	
(-1,-1)	1.5	10	HSDT [49]	526.861	256.776	195.714
			RPT [43]	526.862	256.776	195.714
			Present	526.879	256.784	195.737
	5	HSDT [49]	3772.877	1871.038	1418.120	
		RPT [43]	3772.964	1871.101	1418.193	
		Present	3773.286	1871.237	1418.723	
(-1,1)	0.5	10	HSDT [49]	2772.980	1371.653	1040.519
			RPT [43]	2773.011	1371.265	1040.304
			Present	2773.235	1371.359	1040.652
	5	HSDT [49]	16216.712	8360.541	6257.811	
		RPT [43]	16219.983	8363.233	6260.038	
		Present	16218.875	8362.728	6264.282	
(-1,1)	1	10	HSDT [49]	2772.980 <sup>a</sup>	1371.653 <sup>a</sup>	1040.519 <sup>a</sup>
			RPT [43]	2773.011 <sup>a</sup>	1371.265 <sup>a</sup>	1040.304 <sup>a</sup>
			Present	2773.235 <sup>a</sup>	1371.359 <sup>a</sup>	1040.652 <sup>a</sup>
	5	HSDT [49]	16216.712 <sup>a</sup>	8360.541 <sup>a</sup>	6257.811 <sup>a</sup>	
		RPT [43]	16219.983 <sup>a</sup>	8363.233 <sup>a</sup>	6260.038 <sup>a</sup>	
		Present	16218.875 <sup>a</sup>	8362.728 <sup>a</sup>	6264.282 <sup>a</sup>	
(-1,1)	1.5	10	HSDT [49]	2772.980 <sup>b</sup>	1371.653 <sup>b</sup>	1040.519 <sup>b</sup>
			RPT [43]	2773.011 <sup>b</sup>	1371.265 <sup>b</sup>	1040.304 <sup>b</sup>
			Present	2773.235 <sup>b</sup>	1371.359 <sup>b</sup>	1040.652 <sup>b</sup>
	5	HSDT [49]	16216.712 <sup>b</sup>	8360.541 <sup>b</sup>	6257.811 <sup>b</sup>	
		RPT [43]	16219.983 <sup>b</sup>	8363.233 <sup>b</sup>	6260.038 <sup>b</sup>	
		Present	16218.875 <sup>b</sup>	8362.728 <sup>b</sup>	6264.282 <sup>b</sup>	

a Mode for plate is (m, n) = (2, 1).

b Mode for plate is (m, n) = (3, 1).

### CONCLUSIONS

Mechanical buckling analysis of simply supported FGM plates has been analyzed using a new four-

variable refined plate theory. The number of primary variables in this theory is even less than that of first- and higher-order shear deformation plate theories. The theory gives a parabolic distribution of transverse shear

strains and satisfies the zero traction boundary conditions on the surfaces of the plate without using shear correction factors. The buckling analysis of FGM plates under different types of mechanical loading is presented. Closed-form solutions for the critical buckling of plates are presented. It is concluded that:

1. It is a displacement-based theory that includes transverse shear effects.
2. The critical buckling loadings obtained using the present theory (with four unknown functions) and other shear deformation plate theories (with five unknown functions) are almost identical.

3. Transverse shear stress satisfies perfectly zero shear stress boundary conditions on top and bottom surfaces of the plate.
4. The theory obviates the need of shear correction factor.
5. The critical buckling load for the functionally graded plates is reduced when the power law index  $k$  increases.
6. The critical buckling load of plate under uniaxial compression is greater than that under biaxial compression and less than that under biaxial compression and tension.

### Appendix 1

The displacement field of the classical thin plate theory (CPT) is obtained easily by setting  $\Psi(z) = 0$ . The displacement of the first-order shear deformation plate theory (FSDPT) is obtained by setting  $\Psi(z) = z$  (Reissner, 1945; Reissner, 1944; Mindlin, 1951). Also, the displacement of parabolic shear deformation plate theory (PSDPT) of Reddy (1984) is obtained by setting:

$$\Psi(z) = z \left( 1 - \frac{4z^2}{3h^2} \right) \quad (1)$$

The sinusoidal shear deformation plate theory (SSDPT) of Touratier (1991) is obtained by setting:

$$\Psi(z) = \frac{h}{\pi} \sin\left(\frac{\pi z}{h}\right) \quad (2)$$

In addition, the exponential shear deformation plate theory (ESDPT) of Karama et al. (2003) is obtained by setting:

$$\Psi(z) = ze^{-2(z/h)^2} \quad (3)$$

### Appendix 2

$$g(z) = 1 - \frac{\cosh\left(\frac{\pi}{h}z\right) - 1}{\left[\cosh(\pi/2) - 1\right]}$$

$$f'(z) = \frac{\cosh\left(\frac{\pi}{h}z\right) - 1}{\left[\cosh(\pi/2) - 1\right]}$$

### Appendix 3

$$s_{11} = A_{11} \frac{\partial^2 u}{\partial x^2} + A_{66} \frac{\partial^2 u}{\partial y^2} = A_{11} \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} U_{mn} \cos \lambda x \sin \mu y}{\partial x^2} + A_{66} \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} U_{mn} \cos \lambda x \sin \mu y}{\partial y^2}$$

$$s_{12} = (A_{12} + A_{66}) \frac{\partial^2 v}{\partial x \partial y} = (A_{12} + A_{66}) \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} V_{mn} \sin \lambda x \cos \mu y}{\partial x \partial y}$$

$$s_{13} = -B_{11} \frac{\partial^3 w_b}{\partial x^3} - (B_{12} + 2B_{66}) \frac{\partial^3 w_b}{\partial x \partial y^2}$$

$$= -B_{11} \frac{\partial^3 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{bmn} \sin \lambda x \sin \mu y}{\partial x^3} - (B_{12} + 2B_{66}) \frac{\partial^3 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{bmn} \sin \lambda x \sin \mu y}{\partial x \partial y^2}$$

$$s_{14} = -B_{11}^s \frac{\partial^3 w_s}{\partial x^3} - (B_{12}^s + 2B_{66}^s) \frac{\partial^3 w_s}{\partial x \partial y^2}$$

$$= -B_{11}^s \frac{\partial^3 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial x^3} - (B_{12}^s + 2B_{66}^s) \frac{\partial^3 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial x \partial y^2}$$

$$s_{22} = A_{66} \frac{\partial^2 v}{\partial x^2} + A_{22} \frac{\partial^2 v}{\partial y^2} = A_{66} \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} V_{mn} \sin \lambda x \cos \mu y}{\partial x^2} + A_{22} \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} V_{mn} \sin \lambda x \cos \mu y}{\partial y^2}$$

$$s_{23} = -B_{22} \frac{\partial^3 w_b}{\partial y^3} - (B_{12} + 2B_{66}) \frac{\partial^3 w_b}{\partial x^2 \partial y}$$

$$= -B_{22} \frac{\partial^3 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{bmn} \sin \lambda x \sin \mu y}{\partial y^3} - (B_{12} + 2B_{66}) \frac{\partial^3 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{bmn} \sin \lambda x \sin \mu y}{\partial x^2 \partial y}$$

$$s_{24} = -B_{22}^s \frac{\partial^3 w_s}{\partial y^3} - (B_{12}^s + 2B_{66}^s) \frac{\partial^3 w_s}{\partial x^2 \partial y}$$

$$= -B_{22}^s \frac{\partial^3 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial y^3} - (B_{12}^s + 2B_{66}^s) \frac{\partial^3 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial x^2 \partial y}$$

$$\begin{aligned}
s_{33} &= -D_{11} \frac{\partial^4 w_b}{\partial x^4} - 2(D_{12} + 2D_{66}) \frac{\partial^4 w_b}{\partial x^2 \partial y^2} - D_{22} \frac{\partial^4 w_b}{\partial y^4} + N_x^0 \frac{\partial^2 w_b}{\partial x^2} + N_y^0 \frac{\partial^2 w_b}{\partial y^2} \\
&= -D_{11} \frac{\partial^4 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{bmn} \sin \lambda x \sin \mu y}{\partial x^4} - 2(D_{12} + 2D_{66}) \frac{\partial^4 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{bmn} \sin \lambda x \sin \mu y}{\partial x^2 \partial y^2} - \\
&\quad D_{22} \frac{\partial^4 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{bmn} \sin \lambda x \sin \mu y}{\partial y^4} + N_x^0 \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{bmn} \sin \lambda x \sin \mu y}{\partial x^2} \\
&\quad + N_y^0 \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{bmn} \sin \lambda x \sin \mu y}{\partial y^2} \\
s_{34} &= -D_{11}^s \frac{\partial^4 w_s}{\partial x^4} - 2(D_{12}^s + 2D_{66}^s) \frac{\partial^4 w_s}{\partial x^2 \partial y^2} - D_{22}^s \frac{\partial^4 w_s}{\partial y^4} + N_x^0 \frac{\partial^2 w_s}{\partial x^2} + N_y^0 \frac{\partial^2 w_s}{\partial y^2} \\
&= -D_{11}^s \frac{\partial^4 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial x^4} - 2(D_{12}^s + 2D_{66}^s) \frac{\partial^4 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial x^2 \partial y^2} \\
&\quad - D_{22}^s \frac{\partial^4 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial y^4} + N_x^0 \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial x^2} \\
&\quad + N_y^0 \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial y^2} \\
s_{44} &= -H_{11}^s \frac{\partial^4 w_s}{\partial x^4} - 2(H_{12}^s + 2H_{66}^s) \frac{\partial^4 w_s}{\partial x^2 \partial y^2} - H_{22}^s \frac{\partial^4 w_s}{\partial y^4} + A_{55}^s \frac{\partial^2 w_s}{\partial x^2} + A_{44}^s \frac{\partial^2 w_s}{\partial y^2} + N_x^0 \frac{\partial^2 w_s}{\partial x^2} + N_y^0 \frac{\partial^2 w_s}{\partial y^2} \\
&= -H_{11}^s \frac{\partial^4 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial x^4} - 2(H_{12}^s + 2H_{66}^s) \frac{\partial^4 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial x^2 \partial y^2} \\
&\quad - H_{22}^s \frac{\partial^4 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial y^4} + A_{55}^s \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial x^2} + A_{44}^s \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial y^2} \\
&\quad + N_x^0 \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial x^2} + N_y^0 \frac{\partial^2 \sum_{m=1}^{\infty} \sum_{n=1}^{\infty} W_{smn} \sin \lambda x \sin \mu y}{\partial y^2}
\end{aligned}$$

## REFERENCES

- Ambartsumian, S.A. (1958). "On the theory of bending plates". *Izv. Otd. Tech. Nauk AN SSSR*, 5, 69-77.
- Aydogdu, M. (2009). "A new shear deformation theory for laminated composite plates". *Composite Structures*, 89, 94-101.
- Bhimaraddi, A., and Stevens, L.K. (1984). A higher-order theory for free vibration of orthotropic, homogeneous and laminated rectangular plates". *Journal of Applied Mechanics*, 51 195-198.
- Bodaghi, M., and Saidi, A.R. (2010) "Levy-type solution for buckling analysis of thick functionally graded rectangular plates based on the higher-order shear deformation plate theory". *Applied Mathematical Modelling*, 34 (11), 3659-3673.
- Bouazza, M., and Adda-Bedia, E.A. (2013). "Elastic stability of functionally graded rectangular plates under mechanical and thermal loading". *Academic Journals, Scientific Research and Essays*, 8 (39), 1933-1943, ISSN 1992-2248.
- Bouazza, M., Tounsi A., Adda-Bedia, E.A., and Megueni, A. (2009). "Buckling analysis of functionally graded plates with simply supported edges". *Leonardo Journal of Sciences*, (15), 21-32. ISSN: 1583-0233.
- Bouazza, M., Tounsi, A., Adda-Bedia, E.A., and Megueni, A. (2010). "Thermoelastic stability analysis of functionally graded plates: an analytical approach". *Elsevier, Computational Materials Science*, 49, 865-870, ISSN 0927-0256.
- Carrera, E. (2000). "An assessment of mixed and classical theories on global and local response of multi-layered orthotropic plates". *Composite Structures*, 50, 183-198.
- Carrera, E. (2000). "An assessment of mixed and classical theories for the thermal stress analysis of orthotropic multi-layered plates". *Journal of Thermal Stresses*, 23, 797-831.
- Carrera, E. (2001). "Developments, ideas and evaluations based upon Reissner's mixed variational theorem in the modeling of multi-layered plates and shells". *Applied Mechanics Reviews*, 54, 301-329.
- Carrera, E. (2003). "Historical review of zigzag theories for multi-layered plates and shells". *Applied Mechanics Reviews*, 56, 287-308.
- Delale, F., and Erdogan, F. (1983). "The crack problem for a non-homogeneous plane". *Journal of Applied Mechanics*, 50, 609.
- Hanna, N.F., and Leissa, A.W. (1994). "A higher order shear deformation theory for the vibration of thick plates". *Journal of Sound and Vibration*, 170, 545-555.
- Hosseini-Hashemia, S., Khorshidia, K., and Amabili, M. (2008). "Exact solution for linear buckling of rectangular Mindlin plates". *Journal of Sound and Vibration*, 315, 318-342.
- Kant, T. (1982). "Numerical analysis of thick plates". *Computer Methods in Applied Mechanics and Engineering*, 31, 1-18.
- Karama, M., Afaq, K.S., and Mistou, S. (2003). "Mechanical behaviour of laminated composite beam by new multi-layered laminated composite structures' model with transverse shear stress continuity". *International Journal of Solids and Structures*, 40, 1525-1246.
- Kaysser, W.A., and Ilschner, B. (1995). "FGM research activities in Europe". *MRS Bulletin*, 20 (1), 22-26.
- Kim, S.E., Thai, H.T., and Lee, J. (2009). "Buckling analysis of plates using the two-variable refined plate theory". *Thin-Walled Structures*, 47 (4), 455-462.
- Koizumi, M. (1997). "FGM activities in Japan". *Composites, Part B* 28, 1-2, 1-4.
- Koizumi, M., and Niino, M. (1995). "Overview of FGM research in Japan". *MRS Bulletin*, 20 (1), 19-21.
- Leissa, A.W. (1973). "The free vibration of rectangular plates". *Journal of Sound and Vibration*, 31, 257-293.
- Lo, K.H., Christensen, R.M., and Wu, E.M. (1977). "A high-order theory of plate deformation. Part 1: Homogeneous plates". *Journal of Applied Mechanics*, 44, 663-668.
- Mechab, I., Atmane, H.A., Tounsi, A., Belhadj, H.A., and Bedia, E.A.A. (2010). "A two-variable refined plate theory for the bending analysis of functionally graded plates". *Acta Mechanica Sinica* 26 (6) (2010) 941-949.

- Meisam, M., Ali, R.S., and Emad, J. (2009). "Levy solution for buckling analysis of functionally graded rectangular plates". *International Journal of Applied Composite Materials*, DOI 10.1007/s10443-009-9100-z, Springer Science + Business Media B.
- Mindlin, R.D. (1951). "Influence of rotary inertia and shear on flexural motions of isotropic elastic plates". *Transactions of ASME Journal of Applied Mechanics*, 18, 31-38.
- Mizusawa, T. (1993). "Buckling of rectangular Mindlin plates with tapered thickness by the spline strip method". *International Journal of Solids and Structures*, 30, 1663-1677.
- Murakami, H. (1986). "Laminated composite plate theory with improved in-plane responses". *Journal of Applied Mechanics*, 53, 661-666.
- Praveen, G.N., and Reddy, J.N. (1998). "Non-linear transient thermal elastic analysis of functionally graded ceramic-metal plates". *International Journal of Solids and Structures*, 35 (33), 4457-4476.
- Reddy, J.N. (1984). "A simple higher-order theory for laminated composite plates". *Journal of Applied Mechanics*, 51, 745-752.
- Reddy, J.N., and Phan, N.D. (1985). "Stability and vibration of isotropic, orthotropic and laminated plates according to higher-order shear deformation theory". *Journal of Sound and Vibration*, 98, 157-170.
- Reissner, E. (1944). "On the theory of bending of elastic plates". *Journal of Mathematical Physics*, 23, 184-191.
- Reissner, E. (1945). "The effect of transverse shear deformation on the bending of elastic plates". *J. Applied Mechanics*, 12, 69-77.
- Reissner, E. (1984). "On a certain mixed variational theory and proposed applications". *International Journal for Numerical Methods in Engineering*, 20, 1366-1368.
- Reissner, E. (1986). "On a mixed variational theorem and on a shear deformable plate theory". *International Journal for Numerical Methods in Engineering*, 23, 193-198.
- Shimpi, R.P. (2002). "Refined plate theory and its variants". *AIAA J.*, 40 (1), 137-146.
- Shimpi, R.P., and Patel, H.G. (2006). "A two-variable refined plate theory for orthotropic plate analysis". *International Journal of Solids and Structures*, 43 (22), 6783-6799.
- Shimpi, R.P., and Patel, H.G. (2006). "Free vibrations of plate using two-variable refined plate theory". *Journal of Sound and Vibration*, 296 (4-5), 979-999.
- Shufrin, I., and Eisenberger, M. (2005). "Stability and vibration of shear deformable plates- first-order and higher-order analyses". *International Journal of Solids and Structures*, 42, 1225-1251.
- Soldatos, K.P. (1992). "A transverse shear deformation theory for homogeneous monoclinic plates". *Applied Mechanics*, 94, 195-200.
- Soldatos, K.P., and Timarci, T. (1993). "A unified formulation of laminated composite, shear deformable, five-degrees-of-freedom cylindrical shell theories". *Composite Structures*, 25, 165-171.
- Suresh, S., and Mortensen, A. (1998). "Fundamentals of functionally graded materials". Barnes and Noble Pub.
- Thai, H.T., and Choi, D.H. (2012). "An efficient and simple refined theory for buckling analysis of functionally graded plates". *Applied Mathematical Modelling*, 36, 1008-1102.
- Toledano, A., and Murakami, H. (1987). "A high-order laminated plate theory with improved in-plane responses". *International Journal of Solids and Structures*, 23, 111-131.
- Touratier, M. (1991). "An efficient standard plate theory". *International Journal of Engineering Science*, 29 (8), 901-916.
- Whitney, J.M., and Sun, C.T. (1973). "A higher-order theory for extensional motion of laminated composites". *Journal of Sound and Vibration*, 30, 85-97.
- Xiang, Y. (1993). "Numerical developments in solving the buckling and vibration of Mindlin plates". PhD Thesis, The University of Queensland, Australia.
- Yu, L.H. (2008). "Buckling of rectangular plates on an elastic foundation using the Levy solution". *AIAA*, 46.

Zhou, D., Cheung, Y.K., Au, F.T.K., and Lo, S.H. (2002).  
“Three-dimensional vibration analysis of thick  
rectangular plates using Chebyshev polynomial and

Ritz method”. *International Journal of Solids and  
Structures*, 39, 6339-6353.